

# PRESSURE-INDUCED CLOSURE ON THE JAHN-TELLER DISTORTION IN $\text{Rb}_2\text{CuCl}_4(\text{H}_2\text{O})_2$

F. AGUADO<sup>a</sup>, F. RODRÍGUEZ<sup>\*,a</sup>, R. VALIENTE<sup>b</sup>, J.P. ITIÈ<sup>c</sup> AND P. MUNSCH<sup>c</sup>

<sup>a</sup> DCITIMAC, Facultad de Ciencias, Universidad de Cantabria, Santander 39005, Spain

<sup>b</sup> Departamento de Física Aplicada, Universidad de Cantabria, Santander 39005, Spain

<sup>c</sup> LURE, Centre Universitaire Paris-Sud, 91898 Orsay Cedex, France

This work investigates the pressure-induced variation of the local structure around  $\text{Cu}^{2+}$  as well as the crystal structure in  $\text{Rb}_2\text{CuCl}_4(\text{H}_2\text{O})_2$  through XAS and XRD techniques. The application of pressure induces a structural change in the Jahn-Teller (JT)  $\text{CuCl}_4(\text{H}_2\text{O})_2^{2-}$  complex from axially elongated to compressed. This change leads to the closing of the 2D JT distortion related to the four in-plane  $\text{Cl}^-$  ligands, which are responsible for the antiferrodistortive structure displayed by the crystal. It is shown that the presence of water ligands enhances a JT release. Their associated axial ligand-field favours the occurrence of such a local structural transition below the metallization pressure. The results are compared with recent pressure experiments on  $\text{A}_2\text{CuCl}_4$  systems.

Keywords:  $\text{Cu}^{2+}$ ,  $\text{CuCl}_4(\text{H}_2\text{O})_2$ , Jahn-Teller effect, XRD and XAS under pressure, layer perovskite.

\* Author for correspondence. E-mail: rodriguf@unican.es

## I INTRODUCTION

The presence of  $\text{Cu}^{2+}$  ( $3d^9$ ) or  $\text{Mn}^{3+}$  ( $3d^4$ ) ions either as constituent or impurity in insulating materials gives rise to a great variety of coordination geometries. This is a direct consequence of the Jahn-Teller (JT) effect related to the  $e_g$  hole or electron ground state [1-6]. The occurrence of an elongated geometry around  $\text{Cu}^{2+}$  or  $\text{Mn}^{3+}$  can be explained on the basis of electron phonon coupling between octahedral  $E_g$  electronic states and  $e_g$  vibrations:  $e \otimes E$  JT model In hexacoordinated systems  $\text{CuX}_6^{4-}$  ( $X=\text{H}_2\text{O}$ ,  $\text{NH}_3$ ,  $\text{O}$ ,  $\text{F}$ ,  $\text{Cl}$ ,  $\text{Br}$ ), the observed coordination geometries mostly correspond to low-symmetry elongated octahedra [1-3]. Both the JT distortion and the packing of  $\text{Cu}^{2+}$  complexes strongly influence the optical and magnetic properties of these materials, hence the establishment of structural correlations is crucial for a microscopic characterization [1,2]. Interestingly, the  $e \otimes E$  model predicts that a change of the coordination geometry from elongated to compressed passing through different orthorhombic intermediates, or even JT suppressed can be attained by applying axial stress or hydrostatic pressure. Although there has been an increasing interest to release the JT distortion by applying high pressure, only few experiments were able to show a complete reduction of the JT effect [7-10]. Moreover no clear evidence of this phenomenon was reported so far using local probes [10]. In fact pressure-induced phase transitions observed in  $\text{A}_2\text{CuCl}_4$  (A: alkylammonium ion) by Raman and optical spectroscopy was initially ascribed to structural changes associated with the suppression of the JT distortion [7]. But structural studies performed by X-ray absorption (XAS) and X-ray diffraction (XRD) techniques in  $[\text{C}_3\text{H}_7\text{NH}_3]_2\text{CuCl}_4$  showed that indeed such transformations are mainly related to tilts of the  $\text{CuCl}_6^{4-}$  octahedral rather than to the JT suppression [10]. These pressure results reflect the tendency of the  $\text{CuCl}_6^{4-}$  complex to preserve their *molecular character* associated with the JT distortion. In fact it is due to the higher compressibility of the crystal with respect to the local compressibility of  $\text{CuCl}_6^{4-}$ , whose molecular stiffness is enhanced by the additional binding energy of about 1 eV related to the JT distortion [3].

This work investigates the effect of pressure on the JT distortion of  $\text{Cu}^{2+}$  in the antiferrodistortive (AF)  $\text{Rb}_2\text{CuCl}_4(\text{H}_2\text{O})_2$  through XRD and XAS in the 0-250 kbar range. This compound is interesting since it offers the possibility of exploring structural changes related to the JT effect in isolated heteronuclear complex  $[\text{CuCl}_4(\text{H}_2\text{O})_2]^{2-}$  with elongated rhombic symmetry (Fig.1). The presence of two water ligands exert an axial compression favouring release of the JT distortion at moderate pressures; i.e. below the metallization pressure. This aspect is important in order to establish correlations between the crystal structure and the electronic and vibrational structures from optical spectroscopy.

Our objective is to elucidate whether the application of pressure mainly induces rotation of the  $[\text{CuCl}_4(\text{H}_2\text{O})_2]^{2-}$  distorted octahedra or it is able to suppress the AF structure. This latter case would modify the local structure from an elongated geometry to a compressed situation with four identical Cu-Cl bonds and the short Cu-H<sub>2</sub>O bond as fourfold axis. This behaviour allows us to know how the linear JT electron-phonon coupling in  $\text{Cu}^{2+}$  and high-order interaction terms depend on pressure and consequently how they affect materials properties. In particular, the searched transformation implies a modification of the electronic ground state with the unpaired electron changing from mainly  $d_{x^2-y^2}$  to  $d_{3z^2-r^2}$ . This latter situation is attained in  $[\text{CuCl}_4(\text{NH}_3)_2]^{2-}$  formed in  $\text{Cu}^{2+}$ -doped  $\text{NH}_4\text{Cl}$  by replacing the  $\text{H}_2\text{O}$  axial crystal-field by  $\text{NH}_3$  [11,12].

## II EXPERIMENTAL

Single crystals of  $[\text{CH}_3\text{NH}_3]_2\text{CuCl}_4$ ,  $\text{Rb}_2\text{CuCl}_4$  and  $\text{Rb}_2\text{CuCl}_4(\text{H}_2\text{O})_2$  were grown by slow evaporation from alcoholic solutions following the procedure given elsewhere [13].

XAS experiments under pressure were performed at the absorption setup XAS10 of the D11 beamline at LURE (Orsay). The EXAFS spectra of the investigated  $\text{Rb}_2\text{CuCl}_4(\text{H}_2\text{O})_2$  were measured at the Cu K-edge ( $E_0 = 8.99$  keV) at room temperature using dispersive EXAFS in the 8.9-9.3 keV range. This experimental setup has been proved to be very sensitive for obtaining suitable EXAFS oscillations in a wavelength range where the diamond anvil absorption is very strong. XRD experiments under pressure were done in the energy dispersion setup WDIS of the DW11A beamline at LURE. The XRD and XAS data were analysed by means of the FULLPROF [14] and the WINSAX package programs, respectively.

In both experiments the pressure was applied with a membrane-type diamond anvil cell employing silicon oil as pressure transmitter. The pressure was measured from the R-line shift of Ruby.

## III RESULTS AND DISCUSSION

Fig.1 shows the crystal structure of the  $\text{Rb}_2\text{CuCl}_4$  and the corresponding hydrate  $\text{Rb}_2\text{CuCl}_4(\text{H}_2\text{O})_2$ . Note the different coordination geometry of  $\text{Cu}^{2+}$  in each structure as well as the distinct character of the AF structure. In  $\text{Rb}_2\text{CuCl}_4(\text{H}_2\text{O})_2$ , the  $\text{Cu}^{2+}$  complexes are isolated and do not share any common ligand in contrast to  $\text{Rb}_2\text{CuCl}_4$ , whose interconnected  $\text{CuCl}_6^{4-}$  units form layers.

The XRD and XAS data of Fig.1 allow comparison between the different crystal structure and local structure around  $\text{Cu}^{2+}$  in  $\text{Rb}_2\text{CuCl}_4$  and  $\text{Rb}_2\text{CuCl}_4(\text{H}_2\text{O})_2$ . Apart from differences in XRD, which are associated with the orthorhombic  $Cmca$  and tetragonal  $P4_2/mnm$  structures, respectively,

a salient feature is the different XANES signal observed for each complex. According to previous findings [15,16], the disappearance of the peak around 8.991 keV reveals the change of local structure from  $\text{CuCl}_6^{4-}$  to  $\text{CuCl}_4(\text{H}_2\text{O})_2^{2-}$ . Also the K-edge energy, whose maximum peaks at 8.977 and 8.998 keV, respectively, reveals such difference. The displacement towards high energy observed in the hydrate complex is probably due to the stronger ligand-field produced by the water molecules.

Fig. 2 shows the variation of XAS and XRD corresponding to  $\text{Rb}_2\text{CuCl}_4(\text{H}_2\text{O})_2$  as a function of pressure. The corresponding variations of Cu-Cl and Cu-H<sub>2</sub>O bond distances derived from XAS as well as the crystal and complex volumes in  $\text{Rb}_2\text{CuCl}_4(\text{H}_2\text{O})_2$  as a function of pressure are also included in Fig.2. Interestingly, the pressure behaviour of complex and crystal is rather different. This phenomenon reflects the stiffness of the Cl-Cu and H<sub>2</sub>O-Cu bonds of the JT distorted complex, whose local bulk modulus is an order of magnitude greater than the crystal bulk modulus. A similar result was observed in  $[\text{C}_3\text{H}_7\text{NH}_3]_2\text{CuCl}_4$  for  $\text{CuCl}_6^{4-}$  [10]. However the abrupt change in the Cu-Cl distance observed in  $\text{Rb}_2\text{CuCl}_4(\text{H}_2\text{O})_2$  at 150 kbar is noteworthy. The short Cu-Cl distance slightly increases with pressure whereas the elongated Cu-Cl bond reduces to a common distance,  $R = 2.27 \text{ \AA}$ . This pressure-induced transformation actually corresponds to the searched closure of the JT distortion, leading to a change of the Cu coordination from an elongated rhombic structure to a tetragonal compressed situation above 150 kbar. The associated bond lengths are 2.81 Å and 2.26 Å for Cu-Cl, and 1.97 Å for Cu-H<sub>2</sub>O, in the low-pressure phase, while they are 2.27 Å and 1.96 Å for Cu-Cl and Cu-H<sub>2</sub>O, respectively, in the high-pressure JT-suppressed phase. This change is also accompanied by a crystal phase-transition, which is clearly evidenced by the splitting of the (220) Bragg peak. The origin of this high-pressure phase is currently under investigation.

In conclusion, we demonstrate throughout this work that the JT distortion in  $\text{Cu}^{2+}$  can be more effectively released in axially stressed complexes. In the present case, this situation is attained through the heteronuclear complex  $[\text{CuCl}_4(\text{H}_2\text{O})_2]^{2-}$  whose water ligands favours the local structure transformation to occur at moderate pressures. In fact water molecules provide an intermediate axial ligand-field between that attained in the homonuclear  $\text{CuCl}_6^{4-}$  complex associated with a  $x^2-y^2$  unpaired electron and the heteronuclear tetragonal-compressed  $[\text{CuCl}_4(\text{NH}_3)_2]^{2-}$  complex with  $3z^2-r^2$  ground state. The ammonium ligand-field prevents a 2D JT distortion associated with the Cl ligands [11,12]. A complete account of this research will be reported in a forthcoming publication.

## ACKNOWLEDGMENTS

We thank Dr. Julio Pellicer for fruitful discussions on XAS data. Fernando Aguado is indebted to the MCYT for FPI research grant (Ref. FP99) under CYCIT Project PB98-0190. The XRD and

XAS experiments were done at LURE under proposal (Project PS203-01). This work has been partially financed by the CICYT (Project BFM2001-0695).

## REFERENCES

- [1] M.A. Hitchman, *Comments Inorg. Chem.* **15**, 197 (1994)
- [2] R. Valiente and F. Rodríguez, *J. Phys. Chem. Solids* **57**, 571 (1996)
- [3] R. Valiente and F. Rodríguez, *Phys. Rev. B*, **60**, 9423 (1999)
- [4] D. Oelkrug, *Structure and Bonding* **9**, 1 (1971)
- [5] F. Palacio and M.C. Morón (1992) *Research Frontiers in Magnetochemistry*, World Scientific
- [6] F. Rodríguez, P. Nuñez and M.C. Marco de Lucas *J. Solid State Chem.*, **110**, 370 (1994)
- [7] Y. Moritomo and Y. Tokura, *J. Chem. Phys.* **101**, 1763 (1994)
- [8] I. Loa, P. Adler, A. Grzechnik, K. Syassen, U. Schwarz, M. Hanfland, G. Kh. Rozenberg, P. Gorodetsky, and M. P. Pasternak, *Phys. Rev. Lett.* **87**, 125501 (2001)
- [9] F. Aguado, F. Rodríguez and P. Nuñez, *High Pressure Research* **22**, 121 (2002)
- [10] F. Rodríguez, M. Hanfland, J.P. Itié and A. Polian, *Frontiers of high pressure research II. Application of high pressure to low-dimensional novel electronic materials* Kluwer Academic Publishers **48**, 143 (2001)
- [11] F. Boettcher and J.M. Spaeth, *Phys. Status Solidi b* **61**, 465 (1974)
- [12] A.G. Breñosa, M. Moreno, F. Rodríguez and M. Couzi, *Phys. Rev. B* **44**, 9859 (1991)
- [13] R. Valiente and F. Rodríguez, *J. Phys. Chem. Solids* **57**, 571 (1996)
- [14] J. Rodríguez-Carvajal, FULLPROF Program, Version 3.5d (1998)
- [15] N. Kosugi, T. Yokoyama, K. Asakura and H. Kuroda, *Chem. Phys.* **91**, 249 (1984)
- [16] F. Rodríguez, R. Valiente, J.I. Espeso, M. Benfatto and S. Pascarelli, *High Pressure Research* **18**, 165 (2000)

## FIGURE CAPTIONS


Figure 1

(Top) Crystal structure of  $\text{Rb}_2\text{CuCl}_4$  (*Cmca*) and  $\text{Rb}_2\text{CuCl}_4(\text{H}_2\text{O})_2$  (*P4<sub>2</sub>/mnm*). Only the Cu complexes displaying an AF structure are depicted. (Bottom) Corresponding XRD and XAS results obtained for  $\text{CuCl}_6^{4-}$  and  $\text{CuCl}_4(\text{H}_2\text{O})_2^{2-}$  at ambient conditions.

Figure 2

a) Variation of XAS and XRD for  $\text{Rb}_2\text{CuCl}_4(\text{H}_2\text{O})_2$  as a function of pressure. b) Corresponding distance variation of Cu-Cl ( $R_1$  and  $R_2$ ) and Cu-H<sub>2</sub>O ( $R_3$ ) derived from XAS with pressure. c) Complex volume ( $V_{\text{Cu}} = 1/3 R_1 R_2 R_3$ ) and crystal cell volume ( $V = a^2 c$ ) variation as a function of pressure. The solid lines correspond to the least-square fits to the Murnaghan equation-of-state using  $B_{\text{loc}} = 2300$  (300) kbar, and  $B_{\text{loc}}' = 6$  for the complex, and  $B_0 = 205$  (8) kbar and  $B' = 5.8$  (0.2) for the crystal.

FIG. 1 F. Aguado et al.

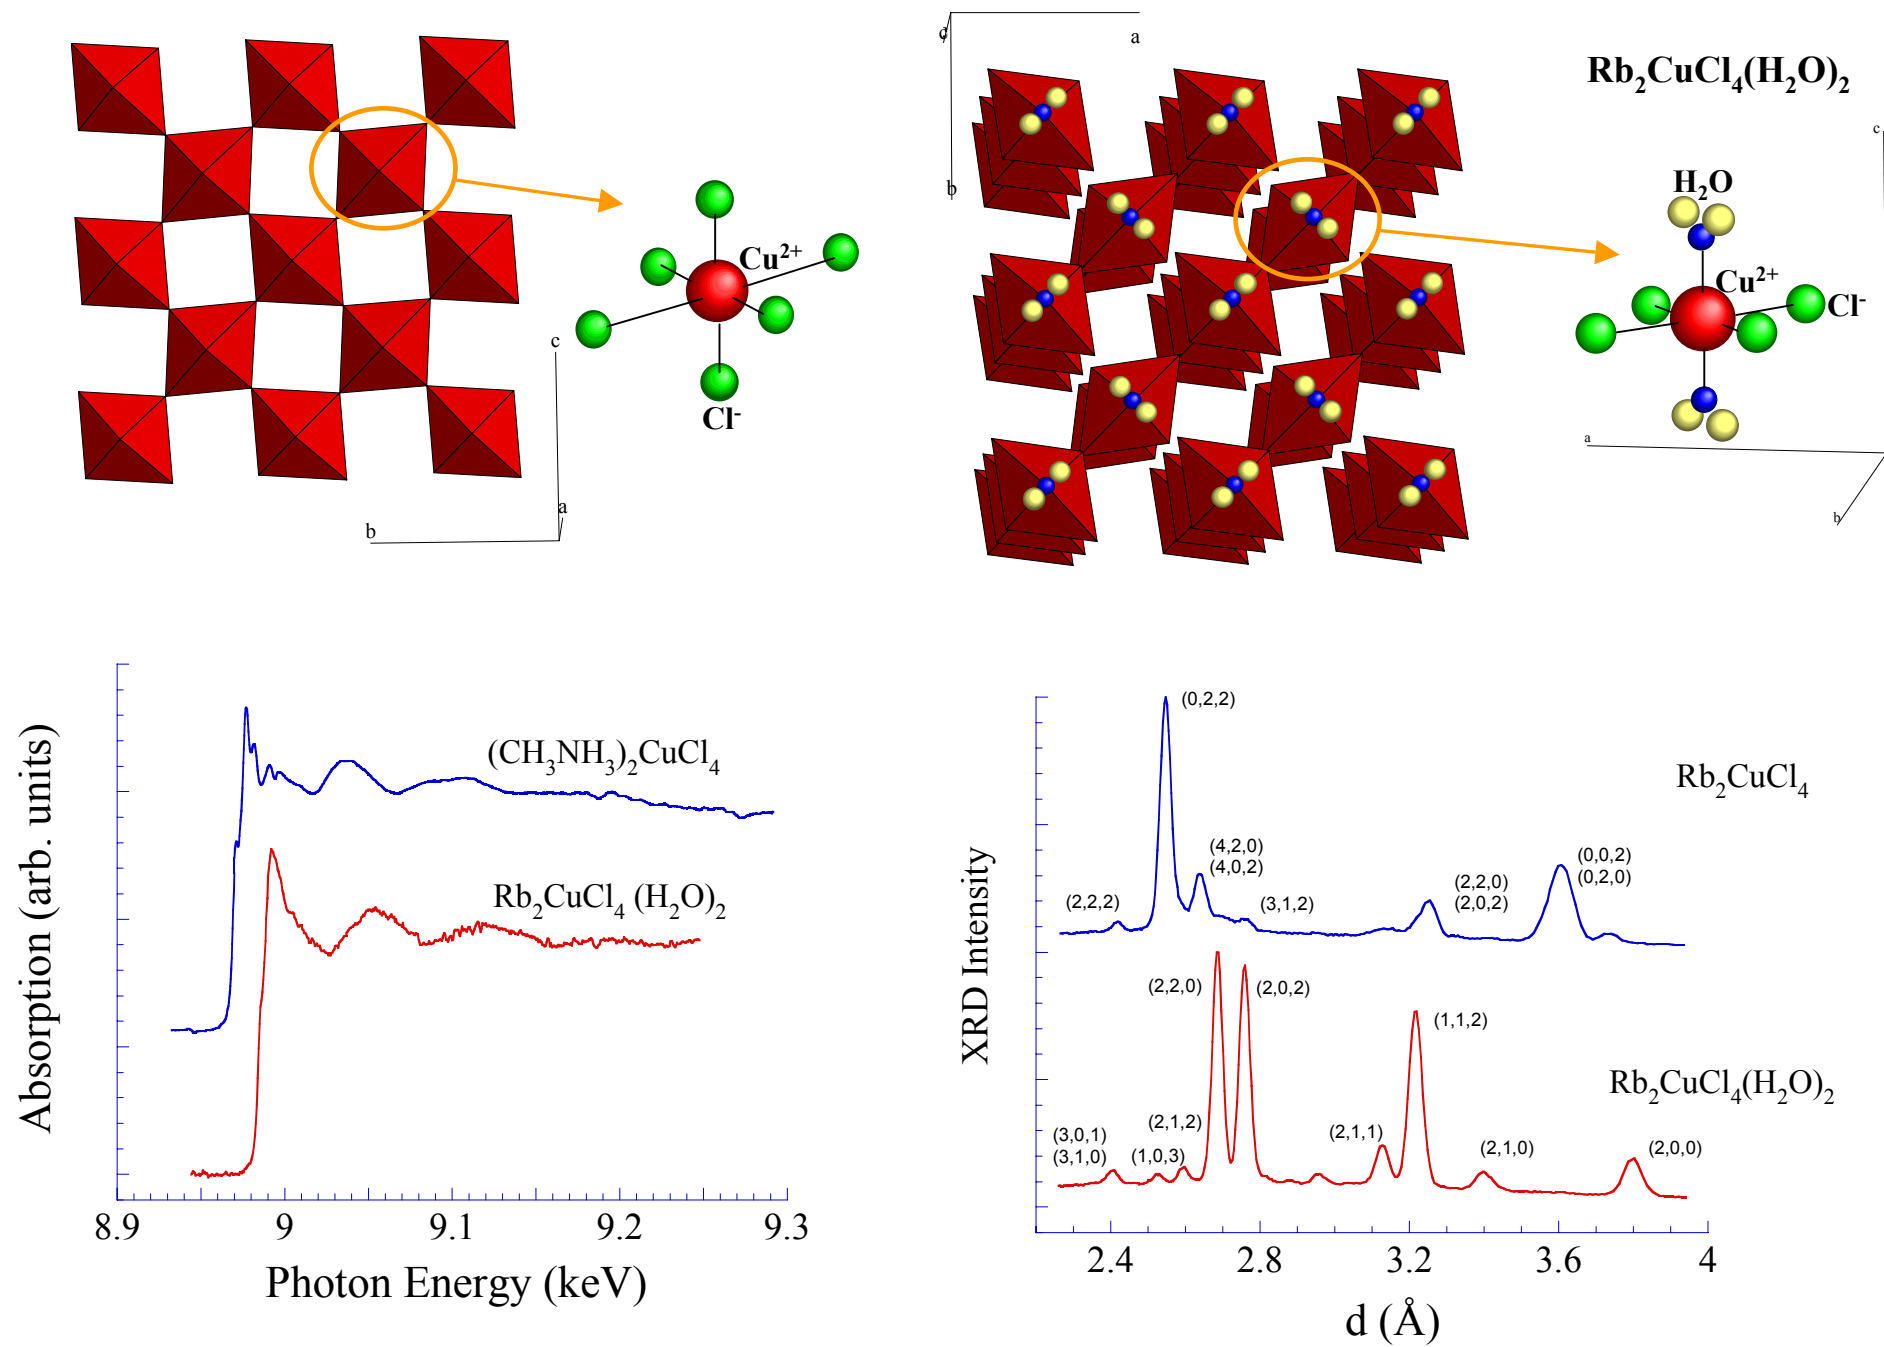

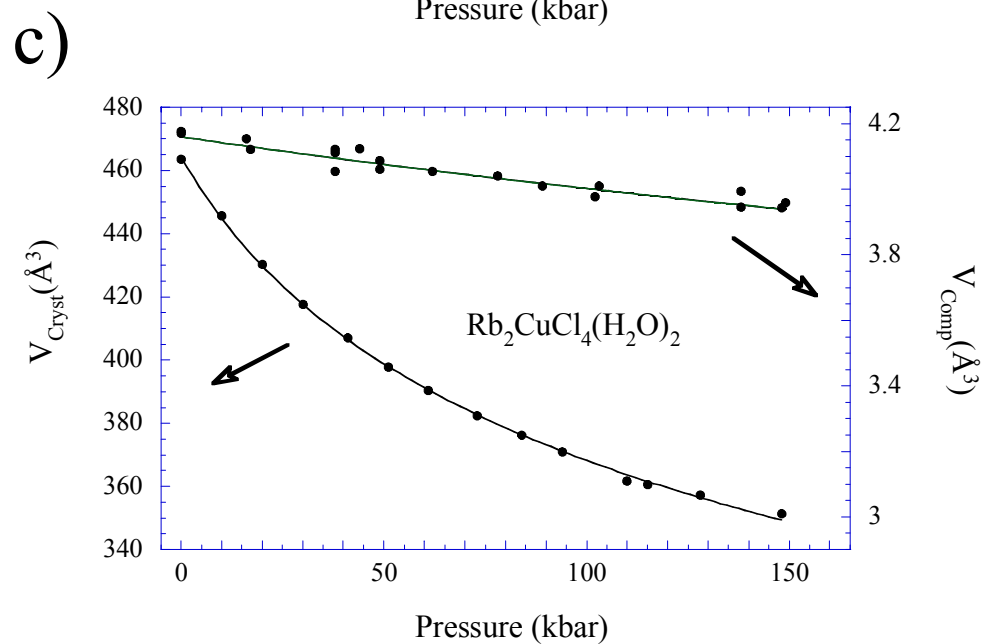
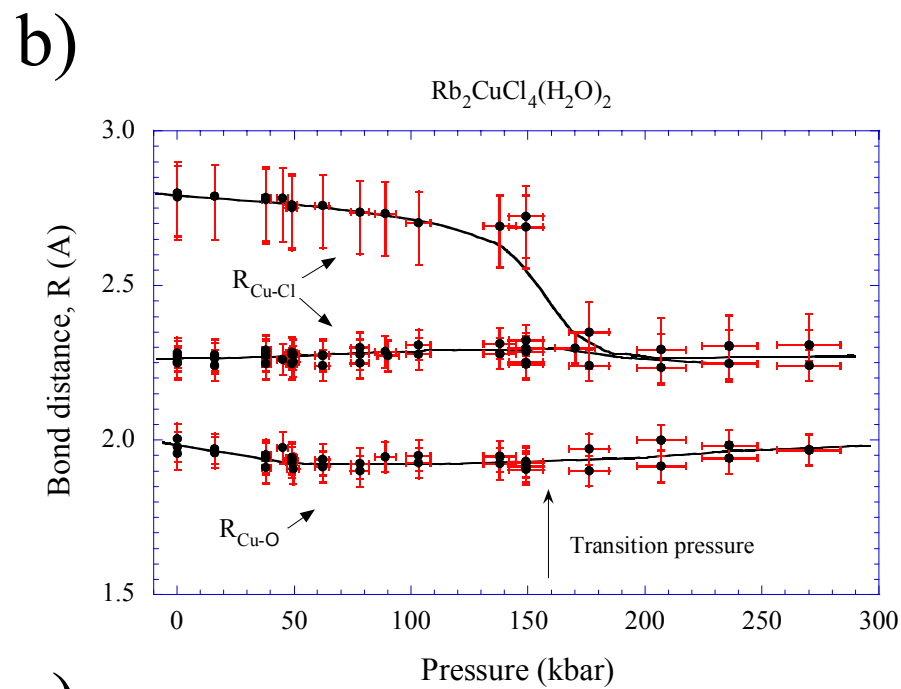
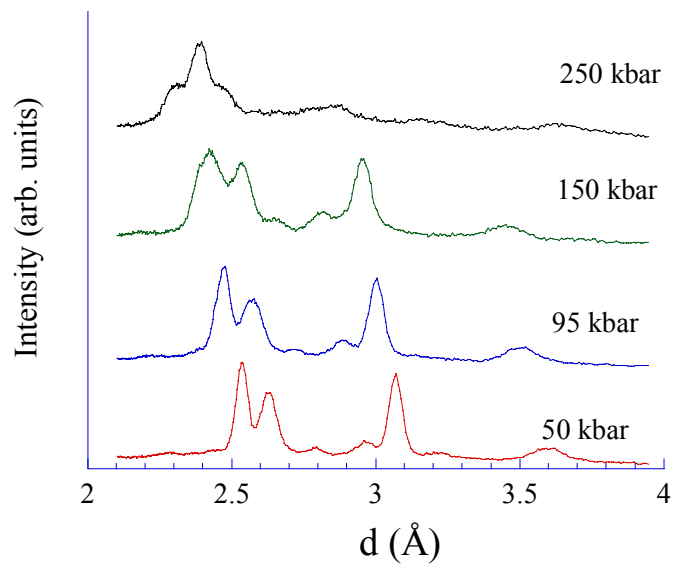
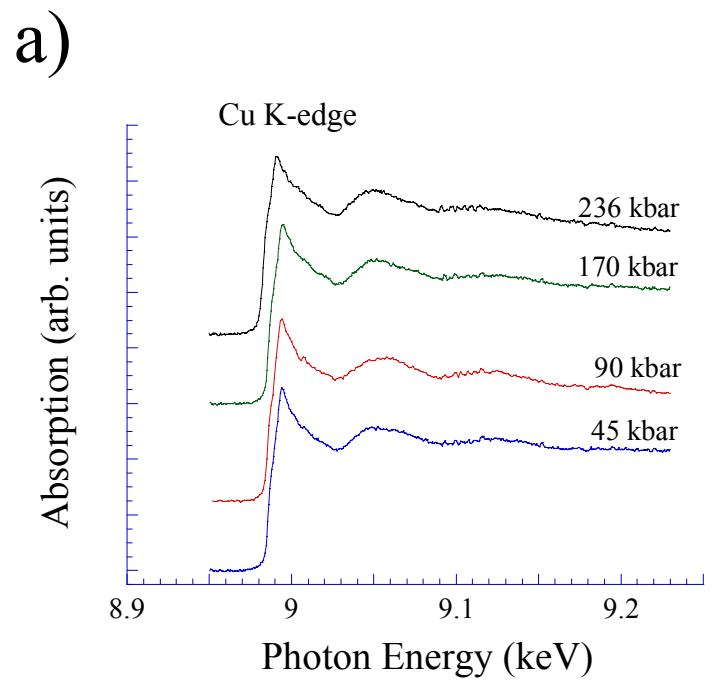


FIG. 2 F. Aguado et al.